

MIL-W-22759/1F
 18 September 1992
 SUPERSEDING
 MIL-W-22759/1E
 10 September 1976

MILITARY SPECIFICATION SHEET

(F) WIRE, ELECTRIC, FLUOROPOLYMER-INSULATED, PTFE AND PTFE-COATED GLASS, SILVER-COATED COPPER CONDUCTOR, 600-VOLT

The requirements for acquiring the product described herein shall consist of this specification sheet and the issue of the following specification listed in that issue of the Department of Defense Index of Specifications and Standards (DODISS) specified in the solicitation: MIL-W-22759.

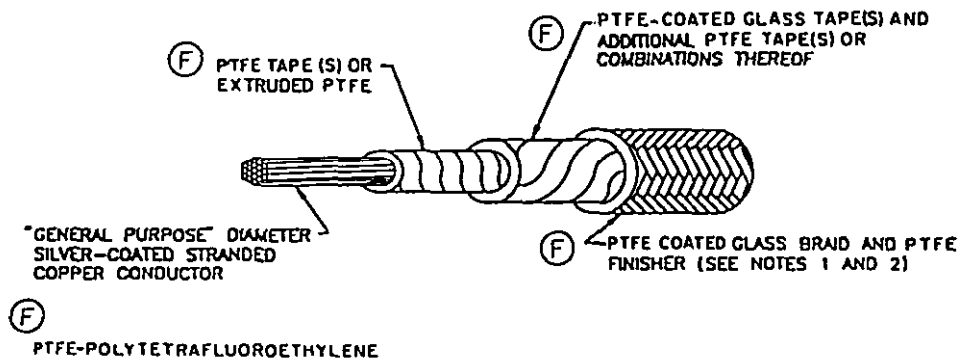


TABLE I. Construction details.

Part No. 1/	Wire size	Stranding (Number of strands x AWG gage of strands)	Diameter of stranded conductor (Inches)		Finished wire		
			(min)	(max)	Resistance at 20°C (68°F) (ohms/1000 ft) (max)	Diameter (inches)	Weight (lbs/1000 ft) (max)
MIL-W-22759/1-22-*	22	19 x 34	.029	.032	15.1	.084 ±.004	7.5
MIL-W-22759/1-20-*	20	19 x 32	.037	.040	9.19	.094 ±.004	9.5
MIL-W-22759/1-18-*	18	19 x 30	.046	.050	5.79	.105 ±.005	13.0
MIL-W-22759/1-16-*	16	19 x 29	.052	.057	4.52	.120 ±.005	16.5
MIL-W-22759/1-14-*	14	19 x 27	.065	.072	2.88	.138 ±.005	23.0
MIL-W-22759/1-12-*	12	37 x 28	.084	.089	1.90	.157 ±.005	32.1
MIL-W-22759/1-10-*	10	37 x 26	.106	.112	1.19	.181 ±.007	47.0
MIL-W-22759/1-8-*	8	133 x 29	.158	.169	.658	.248 ±.007	82.0
MIL-W-22759/1-6-*	6	133 x 27	.198	.213	.418	.293 ±.010	122.
MIL-W-22759/1-4-*	4	133 x 25	.250	.268	.264	.355 ±.015	180.
MIL-W-22759/1-2-*	2	665 x 30	.320	.340	.170	.420 ±.015	275.
MIL-W-22759/1-1-*	1	817 x 30	.360	.380	.139	.470 ±.015	348.
MIL-W-22759/1-01-*	0	1045 x 30	.395	.425	.108	.515 ±.020	429.
MIL-W-22759/1-02-*	00	1330 x 30	.440	.475	.085	.575 ±.020	542.
MIL-W-22759/1-03-*	000	1665 x 30	.500	.540	.068	.640 ±.020	668.
MIL-W-22759/1-04-*	0000	2109 x 30	.565	.605	.054	.710 ±.020	835.

1/ PART NO: The asterisks in the part number column, tables I through III, shall be replaced by color code designators in accordance with MIL-STD-681. Examples: Size 20, white - M22759/4-20-9; white with orange stripe - M22759/4-20-93.

(F) Denotes changes

F

TABLE II. Performance details.

Part No.	Bend testing			Test load (lbs) ($\pm 3\%$)	
	Mandrel diameter (inches) ($\pm 3\%$)				
	Life cycle (oven and bend tests) <u>1/</u>	Cold bend test	Wrap test	Life cycle (oven and bend tests) <u>1/</u>	Cold bend test
M22759/1-22-*	.375	.50	.250	.75	2.0
M22759/1-20-*	.375	.50	.250	.75	2.0
M22759/1-18-*	.50	.75	.375	1.0	2.0
M22759/1-16-*	.50	.75	.375	1.0	3.0
M22759/1-14-*	.625	1.00	.50	1.0	3.0
M22759/1-12-*	.75	2.00	.50	3.0	3.0
M22759/1-10-*	1.00	3.00	.75	3.0	5.0
M22759/1-8-*	2.00	3.00	1.00	3.0	5.0
M22759/1-6-*	3.00	4.00	1.25	6.0	10.0
M22759/1-4-*	4.00	6.00	1.50	6.0	10.0
M22759/1-2-*	6.50	6.00	2.00	6.0	15.0
M22759/1-1-*	10.00	10.00	2.50	6.0	15.0
M22759/1-01-*	10.00	10.00	3.00	10.0	20.0
M22759/1-02-*	10.00	18.00	4.00	10.0	25.0
M22759/1-03-*	10.00	18.00	5.00	10.0	30.0
M22759/1-04-*	10.00	18.00	6.00	10.0	30.0

1/ For bend tests after immersion.

REQUIREMENTS:

Temperature rating: 200°C (392°F) max conductor temperature.

Voltage rating: 600 volts (rms) at sea level.

Spark test of primary insulation: Not required.

Impulse dielectric test: 6.5 kilovolts (peak), 100 percent test.

Insulation resistance: 5,000 megohms for 1000 ft (min).

Wrap test: Mandrel test required - no cracking.

Dielectric test after mandrel wrap, 2500 volt (rms), 60Hz.

Blocking: 260 $\pm 2^\circ\text{C}$ (500 $\pm 3.6^\circ\text{F}$).Shrinkage: 0.125 inch max at 200 $\pm 2^\circ\text{C}$ (392 $\pm 3.6^\circ\text{F}$).

MIL-W-22759/1F

Wicking: Size 22 through 12 - Procedure II; 2.0 percent (max) weight increase, 0.750 inch (max) dye travel.
Size 10 through 0000 - No requirement.

Low temperature (cold bend):

Bend temperature $-65 \pm 2^{\circ}\text{C}$ ($-85 \pm 3.6^{\circ}\text{F}$).

Dielectric test, 2500 volts (rms), 60Hz.

Thermal shock: Oven temperature, $200 \pm 2^{\circ}\text{C}$ ($392 \pm 3.6^{\circ}\text{F}$).

Max change in measurement - Sizes 22 through 12 - 0.060 inch.

Sizes 10 through 8 - 0.100 inch.

Sizes 6 through 0000 - 0.125 inch.

Flammability: Post-flame dielectric test required, 600 volts (rms), 60 Hz.

Life cycle: Oven temperature $313 \pm 2^{\circ}\text{C}$ ($595.4 \pm 3.6^{\circ}\text{F}$).

Dielectric test, 2500 volts (rms), 60Hz.

Dielectric test after immersion: 2500 volts (rms), 60Hz.

Humidity resistance: 5,000 megohms for 1000 ft, min insulation resistance after humidity exposure.

Surface resistance: Sizes 22 through 12 - 500 megohm-inches (min), initial and final readings.

Sizes 10 through 0000 - No requirement.

Smoke: 313°C (595.4°F).

Acid resistance: Required.

Dielectric test, 2500 volts (rms), 60Hz.

Color: In accordance with MIL-STD-104, Class 1; white preferred.

Color striping or banding durability: 50 cycles (100 strokes) (min), 125 grams weight.

Identification durability: 50 cycles (100 strokes) (min), 125 grams weight. Test not required if marking is under clear FEP jacket.

Wire length requirements: Schedule B.

NOTES (INSULATION):

- Ⓕ 1. The PTFE-coated-glass outer braid shall be tightly applied with no gaps apparent when examined visually without the aid of magnification.
2. The insulation, including the outer braid, shall be heat sintered so that it cannot be easily delaminated.

MIL-W-22759/1F

- Ⓕ 3. Caution should be taken during handling and disposal of all insulating and jacketing materials in accordance with ASTM C 930 and FED-STD-313.

Supersession data: The wire of this specification sheet, by part number, replaces and supersedes the wire of MS90294(AS) (canceled) in accordance with table III.

TABLE III. Supersession by part number.

Size designation MIL-W-7139 Class 1	Part number MIL-W-22759/1
22	M22759/1-22-*
20	M22759/1-20-*
18	M22759/1-18-*
16	M22759/1-16-*
14	M22759/1-14-*
12	M22759/1-12-*
10	M22759/1-10-*
8	M22759/1-8-*
6	M22759/1-6-*
4	M22759/1-4-*
2	M22759/1-2-*
1	M22759/1-1-*
0	M22759/1-01-*
00	M22759/1-02-*
000	M22759/1-03-*
0000	M22759/1-04-*

Custodians:
 Army - CR
 Navy - AS
 Air Force - 85

Preparing activity:
 Navy - AS

Review activities:
 Army - AR, ME, MI
 Navy - EC, OS
 Air Force - 99
 DLA - IS
 NASA - NA

Agent:
 DLA - IS

(Project 6145-2000-01)

User activities:
 Army - AT, AV
 Navy - MC